

TEST REPORT

No. : XMIN2211009393CM

Date : Dec 05, 2022

Page: 1 of 6

scan to see the report



XMIN2211009393CM

CUSTOMER NAME: EVERLASTING BASE SDN BHD
ADDRESS: LOT3623-3626 TAMAN PERINDUSTRIAN JASIN ,77200 BEMBAN,
MELAKA, MALAYSIA

Sample Name : SPC6512-3
Manufacturer : EVERLASTING BASE SDN BHD
Material and Mark : SPC

Above information and sample(s) was/were submitted and confirmed by the client. SGS, however, assumes no responsibility to verify the accuracy, adequacy and completeness of the sample information provided by client.

Date of Receipt : Nov 23, 2022
Testing Start Date : Nov 23, 2022
Testing End Date : Dec 05, 2022
Test result(s) : For further details, please refer to the following page(s)
(Unless otherwise stated the results shown in this test report refer only to the sample(s) tested)

Signed for
SGS-CSTC Standards Technical
Services Co. , Ltd Xiamen Branch
Testing Center

Bryan Hong
Authorized signatory



SGS-CSTC Standards Technical Services Co., Ltd.
Xiamen Branch Testing Center Commercial Construction Material Laboratory

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgs.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

TEST REPORT

No. : XMIN2211009393CM


Date : Dec 05, 2022

Page: 2 of 6

Summary of Results:

No.	Test Item	Test Method	Result
1	Peel Strength	ASTM D903-98(2017)	See result
2	Scratch Resistance	Reference to ISO 1518-1:2019 and client's requirement	18.5N
3	Size and Squareness	ASTM F2055-17(2021)	See result
4	Dimensional Stability After Exposure to Heat	ASTM F2199-20	See result
5	Static coefficient of friction	ASTM D2047-17	0.53
6	Locking strength	ISO 24334:2019	See result
7	Abrasion Resistance	EN 13329:2016+A2:2021 Annex E	Average abrasion cycles: 4600 revolutions Abrasion class: AC4

Original Sample Photo:

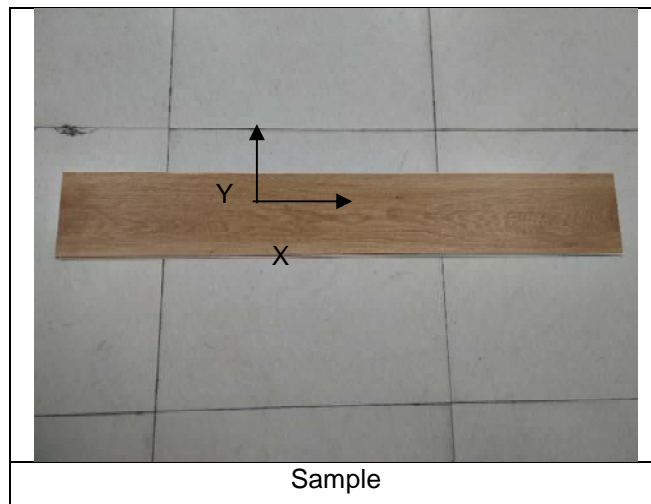

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC Xi'an Branch
Xi'an Branch Testing Center Commercial Construction Material Laboratory

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgsgroup.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

TEST REPORT

No. : XMIN2211009393CM

Date : Dec 05, 2022

Page: 3 of 6

1. Test Item: Peel Strength

Sample Description: see photo

Test Method: ASTM D903-98(2017)

Test Condition:

Specimen width: 25mm

Separation speed: 152.4mm/min

Lab Environmental Condition:(23±2)°C,(50±5)%RH

Test Result:

Test Item	Test Result
Peel Strength	X direction :53.35 N/25mm Y direction :61.48 N/25mm

Note: Test specimens were cut from the sample.

2. Test Item: Scratch Resistance

Sample Description: See photo

Test Method: Reference to ISO 1518-1:2019 and client's requirement

Test Condition:

Rubbing stylus: Scratch stylus B

Stroke: 40 mm

Rubbing Rate: (35±5) mm/s

Test Result:

Sample	Load	Appearance
A	18.5 N	No worn-out to the surface coating

Note:

1. Observation magnification is 4X.
2. Test is along the grain of wood.



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgs.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

TEST REPORT

No. : XMIN2211009393CM

Date : Dec 05, 2022

Page: 4 of 6

3. Test Item: Size and Squareness

Sample Description: See photo

Test Method: ASTM F2055-17(2021)

Test Condition:

Condition the test pieces at a temperature of $(23\pm 1)^\circ\text{C}$ and relative humidity $(50\pm 10)\%$ for a minimum of 24 h.

Test result:

Test item	Length	Width	Squareness
Test result	Ave.: 1220.01mm Max.: 1220.02mm Min.: 1220.01mm	Ave.: 184.01mm Max.: 184.01mm Min.: 183.99mm	0.05mm

Note: All test specimens were cut from the sample.

4. Test Item: Dimensional Stability and Curling after Exposure to Heat

Sample Description: See photo

Test Method: ASTM F2199-20

Test Condition:

Specimen: 305mm×184mm, 3pcs

Condition: $(23\pm 2)^\circ\text{C}$, $(50\pm 5)\%RH$, 24h \rightarrow $(82\pm 2)^\circ\text{C}$, $(6\pm 0.25)\text{h}$ \rightarrow $(23\pm 2)^\circ\text{C}$, $(50\pm 5)\%RH$, 24h

Lab Environment Condition: $(23\pm 2)^\circ\text{C}$, $(50\pm 5)\%RH$

Test Result:

Dimensional stability of X direction: -0.04%

Dimensional stability of Y direction: 0.01%

Curling_{value}: -0.04mm

Curling_{max}: -0.18mm

Note:

- All test specimens were cut from the original samples.
- Dimensional stability, % = (The average final length – The average initial length)/The average initial length × 100.
- Curling, mm = Dimension after exposure to heat - Dimension before exposure to heat.



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC Inspection & Testing Services Co., Ltd.
Xiamen Branch Testing Center Commercial Construction Material Laboratory

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgs.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

TEST REPORT

No. : XMIN2211009393CM

Date : Dec 05, 2022

Page: 5 of 6

5. Test Item: Static coefficient of friction

Sample Description: Flooring, See photo

Test Method: ASTM D2047-17

Test Condition:

Specimen: 300mm×184mm, 3pcs, cut from original sample

Test shoe material: leather

Test speed: 1524mm/min

Testing surface: see photo

Test result:

Dry condition: 0.53

6. Test Item: Locking strength

Sample Description: Flooring, See photo

Test Method: ISO 24334:2019

Test Condition:

Specimen: 200mm×150mm (X Direction) 200mm×150mm (Y Direction), 10 pieces of long side specimens (X Direction), 10 pieces of short side specimens (Y Direction)

Precondition: at (23±2)°C, (50±5)%RH for 24h.

Loading rate: 0.5mm/min

Test result:

Testing direction	Long side(X)	Short side(Y)
Locking strength mean value, kN/m	4.5	4.1



SGS-CSTC Xi'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgsgroup.com.cn
Xiamen Branch Testing Center Commercial Construction Material Laboratory 中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgsgroup.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com

TEST REPORT

No. : XMIN2211009393CM

Date : Dec 05, 2022

Page: 6 of 6

7.Test Item: Abrasion Resistance

Sample Description: Flooring, See photo

Test Method: EN 13329:2016+A2:2021 Annex E

Test Condition:

Specimen: 100mm×100mm, 3pcs

Condition: 23±2°C, 50±5%RH, 24h

Type of wheel: CS-0

Load: 5.4N/wheel

Rotating speed: 60r/min

Abrasive paper strips: S-42(P180)

Test Result:

Average abrasion cycles:4600 revolutions

Abrasion class: AC4

Note:

1. All test specimens were cut from the sample.
2. Abrasion class according to EN 13329:2016+A2:2021 Annex E Table E.1 as follow:

Abrasion class	AC1	AC2	AC3	AC4	AC5	AC6
Average abrasion cycles	≥500	≥1000	≥2000	≥4000	≥6000	>8500

***** End of report*****



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC Xiamen Branch Inspection & Testing Services Co., Ltd.
Xiamen Branch Testing Center Commercial Construction Material Laboratory

No.31 Xianghong Road, Xiang'an Torch Industrial Zone, Xiamen, Fujian Province, China. 361101 t (86-592) 5765857 f (86-592) 5765380 www.sgsgroup.com.cn
中国·福建·厦门·火炬(翔安)产业区翔虹路31号 邮编:361101 t (86-592) 5765857 f (86-592) 5765380 e sgs.china@sgs.com